

Gap Symmetry and Thermal Conductivity in Nodal Superconductors

P. Thalmeier¹ and K. Maki^{2,3}

¹*Max-Planck-Institute for the Chemical Physics of Solids, Nöthnitzer Str.40, 01187 Dresden, Germany*

²*Max-Planck-Institute for the Physics of Complex Systems, Nöthnitzer Str.38, 01187 Dresden, Germany*

³*Department of Physics and Astronomy, University of Southern California, Los Angeles, CA 90089-0484, USA*

Abstract

There are now many nodal superconductors in heavy fermion (HF) systems, charge conjugated organic metals, high T_c cuprates and ruthenates. On the other hand only few of them have well established $\Delta(\mathbf{k})$. We present here a study of the angular dependent thermal conductivity in the vortex state of some of the nodal superconductors. We hope it will help to identify the nodal directions in $\Delta(\mathbf{k})$ of UPd_2Al_3 , UNi_2Al_3 , UBe_{13} and URu_2Si_2 .

PACS numbers: 74.60.Ec, 74.25.Fy, 74.70.Tx

Unconventional superconductivity moved to center stage in recent years [1]. After a long controversy d-wave symmetry of both hole- doped and electron- doped high T_c cuprates has now been established [2,3]. Among HF superconductors the symmetry of $\Delta(\mathbf{k})$ has been identified only for UPt_3 [4,5] and very recently CoCeIn_5 [6]. As to the organic superconductors the symmetry of $\kappa\text{-(ET)}_2\text{Cu(NCS)}_2$ has also been established recently through the angular dependent thermal conductivity in the vortex state [7,8]. Indeed we have shown that the angular dependent thermal conductivity provides a unique window to access the nodal directions in $\Delta(\mathbf{k})$ [8–12]. For example from study of angular dependent thermal conductivity in Sr_2RuO_4 in a magnetic field within the a-b plane, we conclude that the nodal lines do not lie within the a-b plane but along the c- axis possibly at $ck_z=\pm\frac{\pi}{2}$ [13,14]. Recently a number of authors proposed that the nodal lines in UPd_2Al_3 are not in the a-b plane ($ck_z=0$) but somewhere along the c axis [15–18] ($ck_z \neq 0$). The presence of the nodal lines is clearly seen from the low temperature thermal conductivity data [15,19]. Also since UPd_2Al_3 has the hexagonal symmetry, the nodal lines should lie along the c axis. The most obvious possibilities and their associated angular variation of the thermal conductivity will be the focus of this work. It is generally assumed that UPd_2Al_3 is a spin singlet superconductor since it shows a Knight shift reduction below T_c [20–22]. Its magnitude is however difficult to interpret due to contributions of the AF ordered local moments. The excitations of the latter have been identified to mediate the electron pairing in UPd_2Al_3 [18]. Theoretical analysis of this mechanism [23] shows that due to the crystalline electric field anisotropy a nondegenerate odd parity state should be most favorable. It also has a reduced spin susceptibility below T_c and an associated Knight shift. Therefore we include one odd parity nodal gap function with $ck_z=0$ in our discussion. We want to stress that the theory we will develop here will also help to determine the nodal lines in UBe_{13} , URu_2Si_2 and UNi_2Al_3 which has recently been proposed to exhibit odd parity spin triplet pairing [24].

In the following we compute the quasiparticle density of states and the thermal conductivity in a vortex state at low temperature ($T \ll \Delta$) in a magnetic field within the a-c plane. Also we limit ourselves to quasi two dimensional systems where the Fermi surface is approximated by a corrugated cylinder. When the ratio of Fermi velocities $\beta=v_c/v_a$ is not too small, the angular dependent thermal conductivity will tell the nodal position along the k_z - axis.

To calculate the quasiparticle density of states we focus ourselves to nodal superconductors where the nodes lie at some values of $ck_z=\pm\chi_0$. Also for the usefulness of our results $\alpha=(v_c/v_a)^2$ should not be too small (say $\alpha > 0.1$). A magnetic field $\mathbf{H}$ is applied in the a-c plane with an angle θ from the c axis. The supercurrent around vortices is circulating in the plane perpendicular to $\mathbf{H}$. Following Volovik [25], we can handle the effect of the supercurrent within semiclassical approximation. Then the residual density of states is given by [26]

$$g = \text{Re} \left\langle \frac{C_0 - ix}{\sqrt{(C_0 - ix)^2 + f^2}} \right\rangle \quad (1)$$

where $x = |\mathbf{v} \cdot \mathbf{q}|/\Delta$ and $f = \Delta(\mathbf{k})/\Delta$, $C_0 = \lim_{\omega \rightarrow 0} \text{Im}(\tilde{\omega}/\Delta)$, $\tilde{\omega}$ is the renormalized frequency and $\mathbf{k}$ the quasiparticle wave vector. Also $\mathbf{v} \cdot \mathbf{q}$ is the Doppler shift with $\mathbf{v}$ the quasiparticle velocity and $2\mathbf{q}$ the pair momentum, the brackets in the equation above denote the average over the vortex lattice and the Fermi surface. As to f we limit ourselves to three simple cases with odd and even parity gap functions respectively which are appropriate for a Fermi surface model with cylindrical symmetry 1) $f = \sin(ck_z)$, 2) $f = \cos(ck_z)$ and 3) $f = \cos(2ck_z)$. Then for these three cases the average is worked out and we obtain

$$\begin{aligned} g &= \frac{2}{\pi} \left\langle C_0 \ln\left(\frac{2}{\sqrt{C_0^2 + x^2}}\right) + x \tan^{-1}\left(\frac{x}{C_0}\right) \right\rangle \\ &\simeq \langle x \rangle + C_0 (\langle \ln(\frac{2}{x}) \rangle - 1) \quad \text{for } \langle x \rangle \gg C_0 \\ &\simeq C_0 \ln(\frac{2}{C_0}) + \frac{1}{2C_0} \langle x^2 \rangle \quad \text{for } \langle x \rangle \ll C_0 \end{aligned} \quad (2)$$

We call $\langle x \rangle \gg C_0$ and $\langle x \rangle \ll C_0$ the superclean limit and the clean limit respectively [9,11]. Here $\langle \dots \rangle$ means the spatial average over the vortex lattice. Now let us assume that the quasiparticle relaxation is due to impurity scattering in the unitarity limit. Then C_0 is determined by

$$C_0 = \frac{\pi}{2} \frac{\Gamma}{\Delta} g^{-1} \quad (3)$$

Which is solved as

$$\begin{aligned} C_0 &= \frac{\pi}{2} \frac{\Gamma}{\Delta \langle x \rangle} (1 + O(\frac{C_0^2}{\langle x \rangle^2})) \quad \text{for } \langle x \rangle \gg C_0 \\ C_0 &= (\frac{\pi}{2} \frac{\Gamma}{\Delta} \ln(2\sqrt{\frac{2\Delta}{\pi\Gamma}}))^{\frac{1}{2}} (1 - \frac{\Delta}{2\pi\Gamma} \langle x^2 \rangle) \quad \text{for } \langle x \rangle \ll C_0 \end{aligned} \quad (4)$$

Finally the residual density of states is given by

$$\begin{aligned} g &= \langle x \rangle + \frac{\pi}{2} \frac{\Gamma}{\Delta \langle x \rangle} (\langle \ln \frac{2}{x} \rangle - 1) \quad \text{for } \langle x \rangle \gg C_0 \\ g &= g_0 (1 + \frac{\Delta}{2\pi\Gamma} \langle x^2 \rangle) \quad \text{for } \langle x \rangle \ll C_0 \end{aligned} \quad (5)$$

and

$$\begin{aligned} g_0 &= \frac{\pi}{2} \frac{\Gamma}{\Delta} C_0^{-1} \simeq (\frac{\pi}{2} \frac{\Gamma}{\Delta} [\ln(2\sqrt{\frac{2\Delta}{\pi\Gamma}})]^{-1})^{\frac{1}{2}} \\ \langle x \rangle &= \frac{2}{\pi} v_a \sqrt{eH} I(\theta) \\ \langle x^2 \rangle &= \frac{1}{4} v_a^2 (eH) F_c(\theta) \ln\left(\frac{2\Delta}{v_a \sqrt{eH}}\right) \end{aligned} \quad (6)$$

with

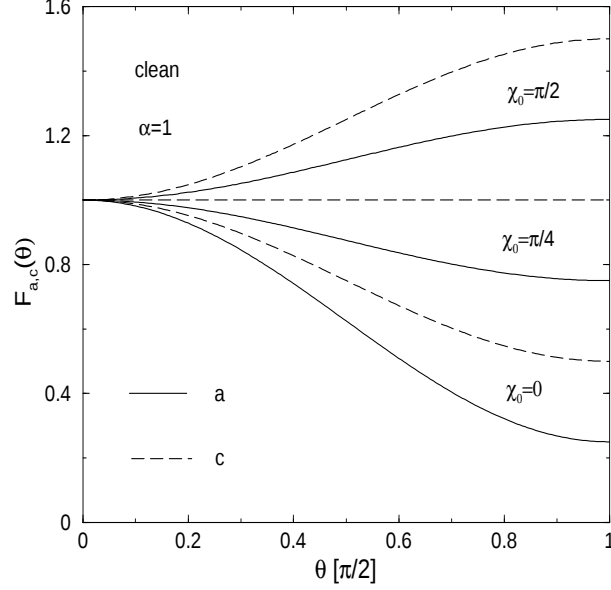


FIG. 1. Angular functions $F_a(\theta)$ and $F_c(\theta)$ in the clean limit and isotropic case ($\alpha=1$) for different node line positions $\chi_0=ck_z$.

$$\begin{aligned}
 I(\theta) &= (\cos^2 \theta + \alpha \sin^2 \theta)^{\frac{1}{4}} \frac{1}{\pi} \int_0^\pi d\phi \\
 &\quad [\cos^2 \theta + \sin^2 \theta (\sin^2 \phi + \alpha \sin^2 \chi_0) \\
 &\quad + \sqrt{\alpha} \sin \chi_0 \cos \phi \sin(2\theta)]^{\frac{1}{2}} \\
 F_c(\theta) &= (\cos^2 \theta + \alpha \sin^2 \theta)^{\frac{1}{2}} [\cos^2 \theta + (\frac{1}{2} + \alpha \sin^2 \chi_0) \sin^2 \theta]
 \end{aligned} \tag{7}$$

where $\alpha=(v_c/v_a)^2$ and $\chi_0=0, \frac{\pi}{2}$ and $\frac{\pi}{4}$ for $f=\sin(ck_z), \cos(ck_z)$ and $\cos(2ck_z)$ respectively. The θ dependence of $F_c(\theta)$ and $G_c(\theta)=I^2(\theta)$ is shown as for $\chi=0, \frac{\pi}{2}$ and $\frac{\pi}{4}$ in the isotropic case $\alpha=1$ in Figs. 1 and 2 (dashed lines). Boundary values for $\chi_0=0$ are given by $F_c(\frac{\pi}{2}) = \frac{1}{2}\sqrt{\alpha} = \frac{1}{2}(\frac{v_c}{v_a})$ and $G_c(\frac{\pi}{2}) = \frac{4}{\pi^2}\sqrt{\alpha}$. Similar curves for the anisotropic case with $\alpha=0.6$ are shown in Figs. 4 and 5 respectively. As noted elsewhere the θ dependent residual density of states is accessible to the specific heat, the superfluid density and the spin susceptibility [9,11]. For example

$$\begin{aligned}
 C_s/\gamma_N T &= g \\
 \chi_s/\chi_N &= g \\
 \rho_s/\rho_s(H=0) &= 1 - g
 \end{aligned} \tag{8}$$

where C_s , χ_s and ρ_s are the electronic specific heat, spin susceptibility and superfluid density in the vortex state respectively. Furthermore γ_N is the Sommerfeld coefficient and χ_N is the Pauli susceptibility in the normal state.

Explicitly the field dependent specific heat is given by

$$C_s/\gamma_N T = \frac{2}{\pi} \frac{v_a \sqrt{eH}}{\Delta} I(\theta)$$

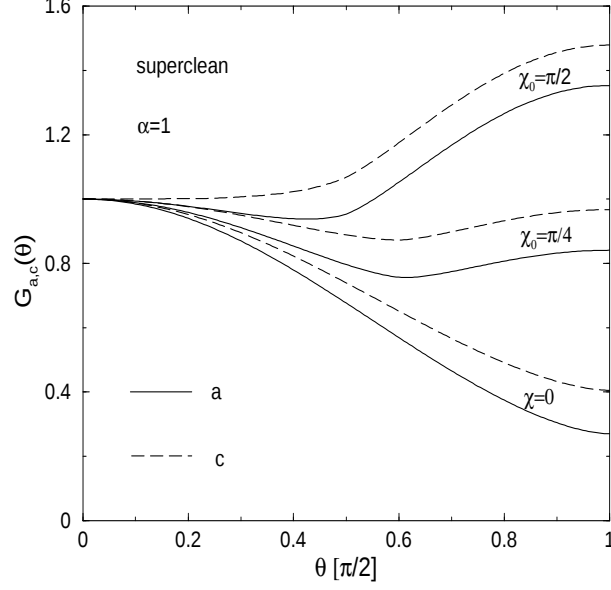


FIG. 2. Angular functions $G_a(\theta) = I(\theta)\tilde{I}(\theta)$ and $G_c(\theta) = I(\theta)^2$ in the superclean limit and isotropic case ($\alpha=1$) for different node line positions $\chi_0 = ck_z$.

$$\begin{aligned}
 & \text{for the superclean limit} \\
 & = \left(\frac{2\Gamma}{\pi\Delta}\right)^{\frac{1}{2}} \left[\ln\left(4\sqrt{\frac{2\Delta}{\pi\Gamma}}\right)\right]^{\frac{1}{2}} \left(1 + \frac{v_a^2(eH)}{8\pi\Gamma\Delta} \ln\left(\frac{\Delta}{v_a\sqrt{eH}}\right) F_c(\theta)\right) \\
 & \text{for the clean limit}
 \end{aligned} \tag{9}$$

In the latter the $C_s(\theta)$ angle dependence is given directly by $F_c(\theta)$ shown in Figs. 1 and 4. For the superclean limit it is given by $I(\theta) = G_c(\theta)^{\frac{1}{2}}$ shown in Fig. 3.

We can now calculate the thermal conductivity within a similar approximation for $T \ll \Delta$ and obtain

$$\begin{aligned}
 \frac{\kappa_c}{\kappa_{nc}} &= \frac{2}{\pi} \frac{v_a^2(eH)}{\Delta^2} I^2(\theta) \\
 & \text{for the superclean limit} \\
 \frac{\kappa_c}{\kappa_{0c}} &= 1 + \frac{v_a^2(eH)}{6\pi\Gamma\Delta} F_c(\theta) \ln\left(2\sqrt{\frac{2\Delta}{\pi\Gamma}}\right) \ln\left(\frac{2\Delta}{v_a\sqrt{eH}}\right) \\
 & \text{for the clean limit}
 \end{aligned} \tag{10}$$

where κ_{nc} is the thermal conductivity in the normal state along the c axis while $\kappa_{0c} = \kappa_c(H=0)$ in the clean limit. The linear H dependence of the heat current is the signature of the superclean limit. In the clean limit, on the other hand, the thermal conductivity starts from the nonvanishing value for $H=0$. Also the H dependence is sublinear in H. Similarly the heat current parallel to the a axis is given by

$$\frac{\kappa_a}{\kappa_{na}} = \frac{2}{\pi} \frac{v_a^2(eH)}{\Delta^2} I(\theta)\tilde{I}(\theta)$$

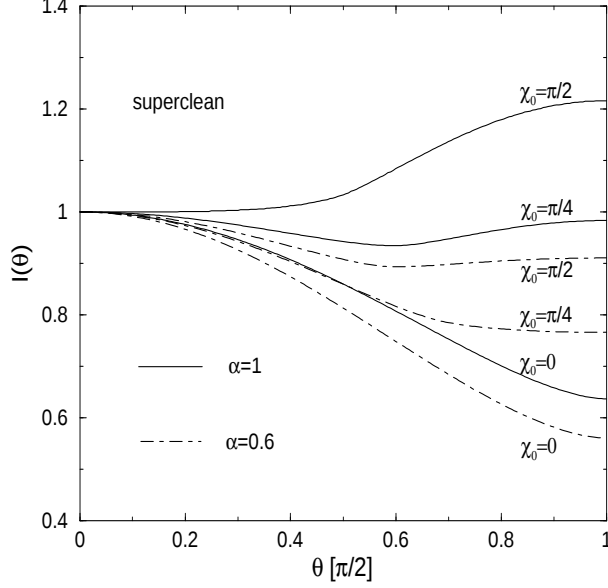


FIG. 3. Angular function $I(\theta)=G_c(\theta)^{\frac{1}{2}} \sim g(\theta)$ which determines the specific heat in the superclean limit for $\alpha=1$ and 0.6 and different node line positions $\chi_0=\text{ck}_z$.

for the superclean limit (11)

$$\frac{\kappa_a}{\kappa_{0a}} = 1 + \frac{v_a^2(eH)}{6\pi\Gamma\Delta} F_a(\theta) \ln\left(2\sqrt{\frac{2\Delta}{\pi\Gamma}}\right) \ln\left(\frac{2\Delta}{v_a\sqrt{eH}}\right)$$

for the clean limit

where

$$\begin{aligned} \tilde{I}(\theta) &= (\cos^2 \theta + \alpha \sin^2 \theta)^{\frac{1}{4}} \frac{1}{\pi} \int_0^\pi d\phi (1 + \cos(2\phi)) \\ &\quad [\cos^2 \theta + \sin^2 \theta (\sin^2 \phi + \alpha \sin^2 \chi_0) \\ &\quad + \sqrt{\alpha} \sin \chi_0 \cos \phi \sin(2\theta)]^{\frac{1}{2}} \\ F_a(\theta) &= (\cos^2 \theta + \alpha \sin^2 \theta)^{\frac{1}{2}} [\cos^2 \theta + (\frac{1}{4} + \alpha \sin^2 \chi_0) \sin^2 \theta] \end{aligned} \quad (12)$$

The θ -dependence of $F_a(\theta)$ and $G_a(\theta)=I(\theta)\tilde{I}(\theta)$ for $\alpha=1$ and $\chi=0, \frac{\pi}{2}$ and $\frac{\pi}{4}$ are shown in Figs. 1 and 2 (full lines) and similar curves for $\alpha=0.6$ in Figs. 4 and 5. The boundary values for $\chi_0=0$ are $F_a(\frac{\pi}{2}) = \frac{1}{4}\sqrt{\alpha}$ and $G_a(\frac{\pi}{2}) = \frac{8}{3\pi^2}\sqrt{\alpha}$. From the superclean limit in both cases a and c in Figs. 2 and 5 we notice that the angular dependence is decidedly nonmonotonic for the even gap function as opposed to the monotonic decrease of $G_{a,c}$ ($\chi_0 \neq 0$) in the odd parity case ($\chi_0=0$). Therefore thermal conductivity measurements in UPd₂Al₃ should be able to decide definitely between the two cases. So far we have neglected the phononic thermal conductivity, which may be easily considered as in [8].

Comparison of $\alpha=1$ and $\alpha=0.6$ results show that the difference in θ -dependent curves $F_{a,c}(\theta)$ and $G_{a,c}(\theta)$ for the various node positions χ_0 becomes smaller with decreasing α . For

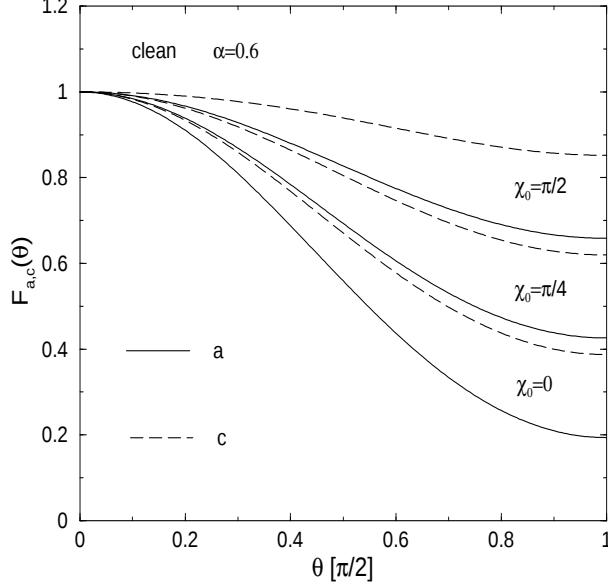


FIG. 4. Angular functions $F_a(\theta)$ and $F_c(\theta)$ in the clean limit and anisotropic case ($\alpha = 0.6$) for different node line positions $\chi_0 = ck_z$.

specific compounds the value of α may be obtained from the upper critical field anisotropy according to $v_c/v_a = H_{c2\parallel}/H_{c2\perp}$. For a small value $\alpha = 0.1$ the difference at $\theta = \frac{\pi}{2}$ (for the various χ_0) becomes also quite small ($\sim 10\%$). This means that in the very anisotropic cases like Sr_2RuO_4 ($\sqrt{\alpha} = \frac{1}{20}$, i.e. $\alpha = 0.0025$) the angular θ dependence therefore can only determine the proper (ab-) plane of node lines [14] but not the position along the c- axis. On the other hand UPd_2Al_3 with $\alpha = 0.69$ is a much more favorable case and the θ - dependence of $\kappa_{a,c}$, C_s should render also the node position along the c- axis.

In conclusion there are many experimental techniques to discover the nodal superconductivity. In particular the $\sqrt{H}$ - dependence of the specific heat provides the clearest signal for it [9,25]. On the other hand to determine the nodal directions in $\Delta(\mathbf{k})$ we need more delicate investigations like the phase sensitive experiments [2,3]. However, the elegant tricrystal experiments appear to not transport to other nodal superconductors aside from high T_c superconductors. In this circumstance the angular dependent thermal conductivity will provide a unique window to look at the nodal directions [8,9]. From the angular dependence of the thermal conductivity Izawa et al have succeeded in deducing the symmetry of $\Delta(\mathbf{k})$ in Sr_2RuO_4 [14], CeCoIn_5 [6] and more recently $\kappa\text{-(ET)}_2\text{Cu(NCS)}_2$ [7]. Therefore it is of great interest to explore this technique to still unidentified order parameter in UPd_2Al_3 , UNi_2Al_3 and other nodal superconductors.

Acknowledgement

We thank Yuji Matsuda for useful discussion on the thermal conductivity in the nodal superconductors and Yoh Kohori for indicating us Refs. [21] and [22]

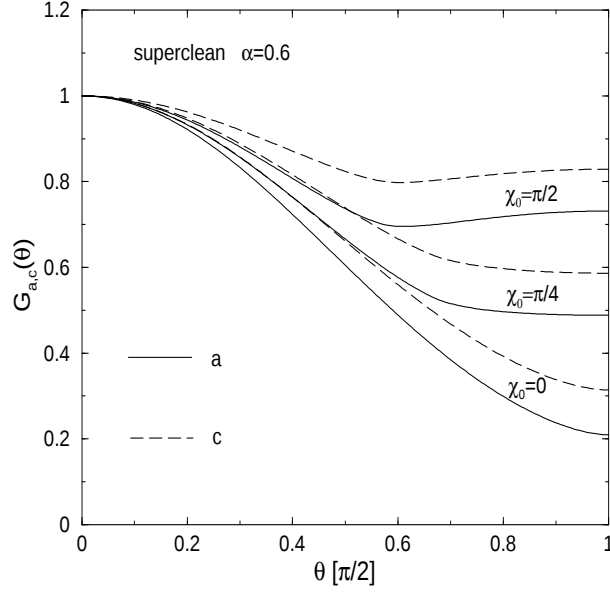


FIG. 5. Angular functions $G_a(\theta) = I(\theta)\tilde{I}(\theta)$ and $G_c(\theta) = I(\theta)^2$ in the superclean limit and anisotropic case ($\alpha=0.6$) for different node line positions $\chi_0 = ck_z$.

REFERENCES

- [1] K. Maki and H. Won in 'Fluctuating Paths and Fields', edited by W. Janke et al (World Scientific, Singapore 2001) pp 457-474; H. Won and K. Maki in 'Symmetry and Pairing in Superconductors' edited by M. Ausloos and S. Kruchinin (Kluwer Academic, Dordrecht 1999) pp 3-9.
- [2] D.J. van Harlingen, Rev. Mod. Phys. 67, 515 (1995)
- [3] C.C. Tsuei and J.R. Kirtley, Rev. Mod. Phys. 72, 469 (2000)
- [4] B. Lussier, B. Ellman, L. Taillefer, Phys. Rev. B 53, 5145 (1996)
- [5] H. Tou, Y. Kitaoka, K. Asayama, N. Kimura, Y. Onuki, E. Yamamoto and K. Maezawa, Phys. Rev. Lett. 77, 1374 (1996)
- [6] K. Izawa, H. Yamaguchi, Y. Matsuda, H. Shishido, R. Settai, and Y. Onuki, Phys. Rev. Lett. 87 57002 (2001)
- [7] K. Izawa, H. Yamaguchi, T. Sasaki and Y. Matsuda, Phys. Rev. Lett., in press (cond-mat/0107537)
- [8] H. Won and K. Maki in Proceedings of SCES' 2001
- [9] H. Won and K. Maki, cond-mat/004105
- [10] T. Dahm, H. Won and K. Maki, cond-mat/006301
- [11] H. Won and K. Maki, Europhys. Lett. 52, 427 (2000); *ibid* 54, 248 (2001)
- [12] H. Won and K. Maki, Current Appl. Phys. (in press)
- [13] M. A. Tanatar, M. Suzuki, S. Nagai, Z. Q. Mao, Y. Maeno, and T. Ishiguro, Phys. Rev. Lett 86, 2649 (2001)
- [14] K. Izawa, H. Takahashi, H. Yamaguchi, Y. Matsuda, M. Suzuki, T. Sasaki T. Fukase, Y. Yoshida, R. Settai and Y. Onuki, Phys. Rev. Lett. 86 2653 (2001)

- [15] M.Chiao, B. Lussier, B.Ellman, L.Taillefer, *Physica B* 230-232, 370 (1997)
- [16] M. Jourdan M. Huth, H. Adrian, *Nature* 398, 47 (1999)
- [17] N. Bernhoeft, N. Sato, B. Roessli, N. Aso, A. Hiess, G. H. Lander, Y. Endoh, and T. Komatsubara *Phys. Rev. Lett.* 81, 4244 (1998)
- [18] N.K. Sato, N. Aso, K. Miyake, R. Shiina, P. Thalmeier, G. Varelogiannis, C. Geibel, F. Steglich, P. Fulde and T. Komatsubara, *Nature* 410, 340 (2001)
- [19] Y. Sun and K. Maki, *Europhys. Lett.* 32, 355 (1995)
- [20] R. Feyerherm, A. Amato, F.N. Gygax, A. Schenck, C. Geibel, F. Steglich, N. Sato and T. Komatsubara, *Phys. Rev. Lett.* 73, 1849 (1994)
- [21] H. Tou, Y. Kitaoka, K. Asayama, C. Geibel, C. Schank and F. Steglich, *J. Phys. Soc. Jpn.* 64, 725 (1995)
- [22] K. Matsuda, Y. Kohori and T. Kohara , *Phys. Rev. B* 55, 15223 (1997)
- [23] P. Thalmeier, cond-mat/0110408
- [24] K. Ishida, D. Ozaki, T. Kamatsuka, H. Tou, M. Kyougaku, Y. Kitaoka, N. Tateiwa, N. K. Sato, N. Aso, C. Geibel and F. Steglich, preprint
- [25] G.E. Volovik, *JETP Lett.* 58, 469 (1993)
- [26] Yu. S. Barash, V.P. Mineev, and A.A Svidzinskii, *JETP* 65, 638 (1997)